

PHYSICAL AND MECHANICAL PROPERTIES OF ATHEL WOOD (*Tamarix aphylla*)

George I. MANTANIS^{1*}

Dimitrios BIRBILIS¹

¹ Technological Education Institute of Larissa, Branch of Karditsa, Department of
Wood and Furniture Design and Technology, Wood Technology Lab, 43100, Karditsa, GREECE.

*mantanis@teilar.gr

ABSTRACT

The aim of this work was to determine the main physical and mechanical properties of athel wood (*Tamarix aphylla*), one of the least studied non-commercial wood species. Wood samples of *Tamarix aphylla* were collected from a small tree stand in Molyvos coastal area (Lesvos, Greece) and standard test methods were followed on small green specimens. Athel wood's air- and oven dry densities were determined at 0.73 and 0.66 g/cm³, while maximum tangential shrinkage and swelling were approximately 10.8 and 12.1%, respectively. The volumetric shrinkage and swelling were estimated at 14.0 and 15.5%, respectively. Modulus of rupture, modulus of elasticity, compression strength parallel to grain and Janka hardness (perpendicular to grain) values were found to be 88.5 N/mm², 7533 N/mm², 40.9 N/mm² and 33.7 N/mm², respectively.

Keywords: Wood, *Tamarix aphylla*, Mechanical properties, Density, Shrinkage, Swelling

ILGIN ODUNUNUN (*Tamarix aphylla*) FİZİKSEL VE MEKANİK ÖZELLİKLERİ

ÖZET

Bu çalışmanın amacı, üzerinde çok az çalışma yapılmış ve ticareti fazla yapılmayan Ilgın (*Tamarix aphylla*) odununun fiziksel ve mekanik özelliklerinin belirlenmesidir. Ilgın odun örnekleri, Molyvos bölgesinin (Midilli, Yunanistan) kıyı kesimlerinden toplanmış ve toplanan örneklere standart test metotları uygulanmıştır. Ilgın odununun hava kurusu ve fırın kurusu yoğunlukları sırası ile 0.3 ve 0.6 g/cm³ olarak belirlenmiş, teğet yönündeki en yüksek daralma ve suda şişme oranları ise %10.8 ve 12.1 olarak hesaplanmıştır. Hacimsel daralma ve şişme oranları ise sırası ile %14.0 ve 15.5 olarak öngörülmüştür. Kopma ve elastik modül ile modülü, liflere paralel direnci ve Janka sertlik değeri ise sırası ile 88.5 N/mm², 7533 N/mm², 40.9 N/mm² ve 33.7 N/mm² bulunmuştur.

Anahtar Kelimeler: Odun, Ilgın, *Tamarix aphylla*, Mekanik özellikler, yoğunluk, Daralma, Şişme

1. INTRODUCTION

Tamarix is a genus of the family *Tamaricaceae* and is composed of 54 species native only in the old world, with one major center of speciation in the Pakistan - Afghanistan - Iran - Turkmenistan - southern Kazakhstan - western China area, and another in the eastern Mediterranean area (Baum, 1978). One of the most known species of this genus is *Tamarix aphylla* which is widespread throughout southeastern Europe, North Africa and Central Asia (Orwa et al., 2009). In Greece and Turkey, this non-commercial species is very common in the coastal areas, beaches and islands mainly in the form of shrubs (Voulgaridis, 2009).

Tamarix aphylla is a fast growing, moderate sized evergreen tree, up to 18 m high with erect tapering trunk, with a ~60-80 cm diameter at breast height and with many stout spreading purplish brown and smooth branches. Its wood is close-grained, light-coloured, fibrous, and fairly hard, with high shock resistance; it also splits readily when first cut and polishes well (Orwa et al., 2009).

Nasir and coworkers (2007) have reported on the general characteristics and structure of athel wood but not on the physical or mechanical properties of it.

Nowadays the end uses of *Tamarix aphylla* wood are diverse. In the USA, athel wood is used for fuel. It is also capable of taking a high polish and has been proposed for fence posts (Tesky, 1992). Moreover, it has been found to be a suitable raw material for making particleboards and can be used as biomass for sugar production (Zheng et al., 2006; Zheng et al., 2007).

Athel wood is additionally utilised for firewood and charcoal (Orwa et al., 2009). It may also be suitable for making ploughs, wheels, carts, tool handles, brush-backs, ornaments, turnery and fruit boxes. Its twigs are used for basket making, while its bark is a rich source of tannins and mordant for dyeing (Orwa et al., 2009). In Turkey, currently, there is not much information available on the properties of athel wood. Determining the properties of athel wood may provide an initial data to the researchers and offer interesting opportunities in future.

Up to date, there has not been any study concentrated on the properties of athel wood. The objective of this work therefore was to determine some of the main physical and mechanical properties of athel wood (*Tamarix aphylla*), of which not detailed previous research had been found in the literature.

2. MATERIALS AND METHODS

Samples of mature wood of *Tamarix aphylla* were cut from 3 trees in Molyvos coastal area, in the island of Lesbos, Greece. These trees had a ~40 cm diameter at breast height. After a slow air drying process of three months, small clear wood specimens were prepared from this material according to Table 1. Specimens were then conditioned at normal climatic conditions, that is, $20\pm 1^{\circ}\text{C}$ and $65\pm 3\%$ relative humidity (RH), for a period of twelve weeks.

Preparation of cross sections: Wood blocks (20 x 20 x 20 mm) taken from the specimens were softened by boiling in water for 4 h. After the complete softening of the wood blocks, cross sections were cut using a sliding microtome and prepared at a magnification of ~20X.

Measurements of physical properties: Density was determined according to DIN EN 52182 standard under two conditions: oven-dry (at ~0% moisture content) and air-dry condition. The maximum shrinkage, that is, the directional change from the fiber saturation point until the oven-dry condition, was measured in fifteen specimens according to DIN EN 52184 standard. Specimens with moisture content above the fiber saturation point were collected and their tangential and radial anatomical dimensions were recorded. Subsequently, the specimens were dried in an air-circulating oven at $103\pm 2^\circ\text{C}$ until constant mass weights.

Following the shrinkage tests, the maximum swelling of the same wood specimens was measured. Oven-dry volume and mass were recorded for each specimen during the first set of experiments (shrinkage tests). Thereafter, each specimen was slowly wetted with water using an absorbing paper. This allowed each specimen to slowly absorb water until it reached a point where its weight corresponded to a ~30% moisture content level (i.e. fiber saturation point), as projected out of its initial oven-dry mass.

Table 1. Information on the testing of *Tamarix aphylla* wood.

Property	Number of specimens	Dimensions of specimens*	Standard
Density, air-dry	15	40 x 20 x 20	DIN 52182
Density, oven-dry	15	40 x 20 x 20	DIN 52182
Shrinkage & swelling	15	10 x 20 x 20	DIN 52184
Static bending	15	360 x 20 x 20	DIN 52186
Axial compression	20	60 x 20 x 20	DIN 52185
Hardness (Janka test)	20	50 x 50 x 50	ASTM D143-94

* Longitudinal x radial x tangential direction (mm x mm x mm)

Measurements of mechanical properties: The cross section of *Tamarix aphylla* wood is presented in Fig. 1. The growth rings are distinct, and its vessels appear to be small to medium and variable in size, usually solitary and distributed unevenly. The rays are thick and broad conspicuous. These data are in very good agreement with the findings of Nasir et al. (2007).

The mechanical properties of *Tamarix aphylla* wood were evaluated on specimens free from defects under normal climatic conditions ($65\pm 3\%$ RH and $20\pm 1^\circ\text{C}$) in accordance with DIN EN 52186 standard. The results obtained were compared with the properties of ash wood (*Fraxinus sp.*), a commercial species with a similar density.

The static bending tests were performed according to DIN EN 52186 standard. The static modulus of elasticity (MOE) was determined on fifteen specimens by testing static bending strength; the testing for evaluating the modulus of rupture (MOR) was performed with a Zwick-Roell Z020 testing machine. The load was applied at a rate of 5 mm/min. The compression strength in parallel direction to the fiber (axial compression) was evaluated according to DIN EN 52185 standard. In addition, the modified Janka hardness in transverse direction was measured according to ASTM D143-94 standard.

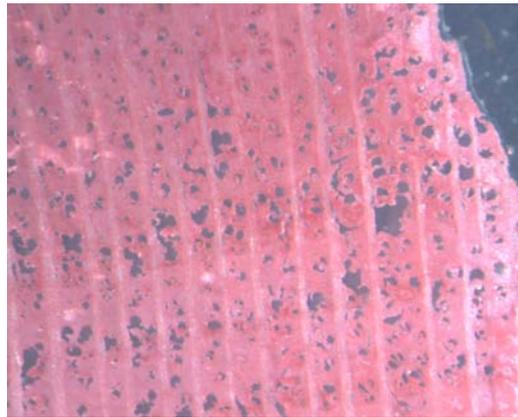


Figure 1. Cross section of *Tamarix aphylla* wood (magnification of ~20X).

3. RESULTS AND DISCUSSIONS

The physical and mechanical properties obtained of *Tamarix aphylla* wood samples are shown in Table 2. The corresponding property values of ash wood (*Fraxinus sp.*) as reported by Tsoumis (1991) are also shown in Table 2 for comparative purposes.

Athel wood's air-dry and oven-dry densities were determined at 0.73 and 0.66 g/cm³, respectively. Volumetric shrinkage was determined at 14%; a little higher as compared with that of ash (13.5%), a wood species with the same density. Tangential shrinkage (10.8%) and swelling (12.1%) of this wood were found to be very high, that is, much higher than its radial shrinkage (3.2%) and swelling (3.4%). Notably this resulted in an extraordinary high tangential/radial ratio (3.8) for this species. For comparison (Table 2), the maximum shrinkage values of ash wood have been reported to be 8.3% in the tangential direction and 5.2% in the radial direction (i.e. tangential/radial ratio: 1.6).

The average MOE of *Tamarix aphylla* wood was 7533 N/mm²; the average MOR value was 88.5 N/mm². These values are very low as compared with those of ash wood (MOE: 13,130 N/mm², MOR: 118 N/mm²) reported by Tsoumis (1991).

Table 2. Physical and mechanical properties of *Tamarix aphylla* wood and comparative literature values of *Fraxinus sp.* wood.

Property	<i>Tamarix aphylla</i> wood ¹	<i>Fraxinus sp.</i> wood ²
Wood density (g/cm ³)		
oven-dry	0.66 (0.03)	0.66
air-dry	0.73 (0.03)	0.70
Shrinkage (%), maximum		
radial	3.2 (1.0)	5.2
Tangential	10.8 (2.1)	8.3
ratio T/R shrinkage	3.8 (1.4)	1.6
Swelling (%), maximum		
radial	3.4 (1.0)	-
tangential	12.1 (2.5)	-
MOE (N/mm ²)	7,533 (1,008)	13,130
MOR (N/mm ²)	88.5 (5.2)	118
Axial compression (N/mm ²)	40.9 (2.3)	51
Janka hardness		
transverse (N/mm ²)	33.7 (2.8)	59

¹ Average value \pm standard deviation. ² Data from Tsoumis (1991)

The axial compression of athel wood was found to be 40.9 N/mm² on the average. Tsoumis (1991) has reported a value of 51.0 N/mm² for axial compression strength of ash wood, which is quite higher than that of athel wood found in this work. The Janka hardness was estimated at ca. 33.7 N/mm² in the transverse direction. This value seems extremely low. Ash wood has been reported in the literature to show much higher Janka hardness values, e.g. 59 N/mm² (Tsoumis, 1991).

4. CONCLUSIONS

This work focused on the main physical and mechanical properties of *Tamarix aphylla* wood. The results showed that the mechanical properties (MOR, MOE, axial compression, Janka hardness) of this wood species are very low as compared with those of ash wood, a known commercial species with equivalent density. In addition, the tangential shrinkage and swelling of *Tamarix aphylla* wood exhibited high values, while the anisotropy between radial and tangential shrinkage estimated to be extremely high. Consequently, *Tamarix aphylla* wood cannot be considered as useful timber for technical uses. Nevertheless, more work on the chemical properties of this wood for its potential for other uses (e.g. biomass, fuelwood) may be of interest..

ACKNOWLEDGEMENT

The authors acknowledge the technical assistance of Mr. Efstratios Voudourellis, from Stipsi, Lesvos, in the preparation of athel wood specimens.

PHYSICAL AND MECHANICAL PROPERTIES OF ATHEL WOOD (*Tamarix aphylla*)

REFERENCES

- ASTM D 143-94, 2005. Standard methods of testing small clear specimens of timber. The ASTM Book of Standards, Philadelphia, PA, USA.
- Baum, B.R., 1978. The Genus *Tamarix*. Israel Academy of Sciences and Humanities, Jerusalem, Israel, pp. 96.
- DIN 52182, 1994. Prüfung von Holz - Probenahme - Grundlagen; DIN-Taschenbuch 31, Beuth, Germany.
- DIN 52184, 1979. Prüfung von Holz; Bestimmung der Quellung und Schwindung. DIN-Taschenbuch 31, Beuth, Germany.
- DIN 52185, 1976. Prüfung von Holz; Bestimmung der Druckfestigkeit parallel zur Faser. DIN-Taschenbuch 31, Beuth, Germany.
- DIN 52186, 1978. Prüfung von Holz; Biegeversuch. DIN-Taschenbuch 31, Beuth, Germany.
- Nasir, G.M., Fatima, N., Suleman, K.M., 2007. Technological properties and suitability determination of some non-commercial timbers on the basis of anatomical properties. Pakistan Forest Institute, Pakistan.
- Orwa, C., Mutua, A., Kindt, R., Jamnadass, R., Anthony, S., 2009. Agroforestry Database: a tree reference and selection guide version 4.0.
- Tesky, J.L., 1992. *Tamarix aphylla*. In: Fire Effects Information System. U.S. Department of Agriculture, Forest Service, Forest Products Laboratory, Madison.
- Tsoumis, G., 1991. Science and technology of wood: Structure, properties, utilization. Van Nostrand Reinhold, New York, USA, pp. 82.
- Voulgaridis, E.V., 2009. Commercial European and tropical woods: structure, properties and uses (in Greek). Aristotle University of Thessaloniki, Greece, pp. 92.
- Zheng, Y., Pan, Z., Zhang, R., Jenkins, B.M., Blunk, S., 2006. Properties of medium-density particleboard from saline Athel wood. *Ind. Crop. Prod.* 23, 318–326.
- Zheng, Y., Pan, Z., Zhang, R., Labavitch, J., Wang, D., Teter, S., Jenkins, B., 2007. Evaluation of different biomass materials as feedstock for fermentable sugar production. *Appl. Biochem. Biotech.* 137-140 (1-12), 423-435.